

Nonlinear response and scaling law in the vortex state of d -wave superconductors

H. WON^{1,2} and K. MAKI²

¹*Department of Physics, Hallym University, Chunchon 200-702, South Korea*

²*Department of Physics and Astronomy, University of Southern California, Los Angeles, CA 90089-0484, USA*

(received ; accepted)

PACS. 74.20.Fg – BCS theory and its development.

PACS. 74.25.Bt – Thermodynamic Properties.

PACS. 74.25.Fy – Transport properties.

Abstract. – We study the field dependence of the quasi-particle density of states, the thermodynamics and the transport properties in the vortex state of d -wave superconductors when a magnetic field is applied perpendicular to the conducting plane, specially for the low field and the low temperature compared to the upper critical field and transition temperature, respectively, $H/H_{c2} \ll 1$ and $T/T_c \ll 1$. Both the superfluid density and the spin susceptibility exhibit the characteristic $\sqrt{H}$ -field dependence, while the nuclear spin lattice relaxation rate T_1^{-1} and the thermal conductivity are linear in field H . With increasing temperature, these quantities exhibit the scaling behavior in $T/\sqrt{H}$. The present theory applies to 2D f -wave superconductor as well; a possible candidate of the superconductivity in Sr_2RuO_4 .

Introduction. – Single crystals of high- T_c cuprate superconductors like YBCO, Bi2212, etc. appear to provide the most useful testing ground for properties of unconventional superconductors[1]. In particular d -wave superconductivity has been established both in the hole-doped and the electron-doped high- T_c cuprates [2, 3, 4]. Due to the nodal structure in the d -wave order parameter, the specific heat[5], the spin susceptibility and the superfluid density[6] have been predicted to behave like $\sqrt{H}$ in the vortex state where H is the magnetic field. Indeed the $\sqrt{H}$ dependence of the specific heat in the vortex state of YBCO has been established [7, 8, 9]. On the other hand, the $\sqrt{H}$ dependence of the superfluid density appears to have not been seen in spite of an elaborate muon spin rotation experiment [10].

In the meantime, the calculational technique greatly improved [11, 12, 13, 14]. Therefore we can study the effect of a magnetic field within the semi-classical approximation almost analytically within the weak-coupling theory of d -wave superconductivity. Most of earlier works considered only the spherical Fermi surface [11, 12, 13]. Here we assume that the Fermi surface of these d -wave superconductors is a weakly modulated cylinder[14]. Then the present model should be also applicable to the recently discovered d -wave superconductors in κ -(ET)₂ salts [15, 16, 17]. The present model applies as well to the superconductivity in Sr_2RuO_4 , if

the superconductivity is one of 2D f -wave states (i.e. $\Delta(\mathbf{k}) \sim e^{\pm i\phi} \cos(2\phi)$, $e^{\pm i\phi} \sin(2\phi)$ or $e^{\pm i\phi} \cos(ck_3)$, where ϕ is the angle between the quasi-particle momentum and a -axis in the plane and k_3 the quasi-particle momentum in the c -direction and c is the distance between layers of conducting plane in the c -direction.) which are considered by Hasegawa *et al.* [18], The specific heat [19]. NMR [20] and the magnetic penetration depth measurement [21] show clearly the presence of the nodal structure [22]. The thermodynamics and the planar transport of these f -wave states are exactly same as the ones in d -wave superconductors when the field is applied perpendicular to the conducting plane.

The object of the present paper is to study the quasi-particle density of states in the vortex state of d -wave superconductors when a magnetic field is applied perpendicular to the conducting plane, specially for the low field and the low temperature compared to the upper critical field and transition temperature, respectively, $H/H_{c2} \ll 1$ and $T/T_c \ll 1$. Then making use of the density of states, we calculate the specific heat, the spin susceptibility, the superfluid density and the nuclear spin lattice relaxation rate T_1^{-1} in NMR. Also for clarity, we limit ourselves to the superclean limit where the effect of impurity scattering is negligible. For $E/\Delta \ll 1$ the quasi-particle density of states is a simple function of $E/\epsilon \sim E/\sqrt{H}$ where E is the energy of a quasi-particle, Δ is the d -wave superconducting order parameter, $\epsilon = v\sqrt{eH}/2$, e electron charge and v the Fermi velocity in the conducting plane. Then in the limit of $T \rightarrow 0$, the specific heat, the spin susceptibility and the change in the superfluid density behave like $\sqrt{H}$, while T_1^{-1} behaves like H . Indeed, the $\sqrt{H}$ dependence of the spin susceptibility and the H linear dependence of T_1^{-1} , are recently observed by NMR in the vortex state of underdoped YBCO [23]. In addition, the thermal conductivity both in the superclean limit and the clean limit will be briefly discussed.

For $T \neq 0$ K, all these quantities exhibit scaling behavior as first discussed by Simon and Lee [24]. Actually the present model gives the explicit scaling functions, which should be readily accessible experimentally.

Quasi-particle density of states. – Following the semi-classical approximation by Volovik[5] the quasi-particle density of states in the the vortex state of d -wave superconductor is given by

$$N(E, H)/N_0 \simeq \frac{1}{\Delta} \langle |E| \vee |\mathbf{v} \cdot \mathbf{q}| \rangle \quad (1)$$

where $|E| \vee |\mathbf{v} \cdot \mathbf{q}|$ means the bigger one among $|E|$ and $|\mathbf{v} \cdot \mathbf{q}|$. Also we assumed $|E|, |\mathbf{v} \cdot \mathbf{q}| \ll \Delta$. Here $|\mathbf{v} \cdot \mathbf{q}|$ is the Doppler shift [25] associated the pair momentum $2\mathbf{q}$ and the Fermi velocity $\mathbf{v}$. In a magnetic field $\mathbf{H} \parallel \mathbf{c}$, the Doppler shift is given as $\mathbf{v} \cdot \mathbf{q} = \frac{v}{2r} \cos \phi$ where r is the distance from the center of the vortex and ϕ is the angle between $\mathbf{v}$ and $\mathbf{q}$. Although $\mathbf{v}$ is parallel to one of nodal lines at low temperature, ϕ runs from 0 to 2π . Finally $\langle \dots \rangle$ of the Eq.(1) means the spatial average over r and ϕ . This average is carried out over a unit cell of a square vortex lattice characteristic to d -wave superconductors [6] *à la* Wigner Seitz.

$$\langle \dots \rangle = \frac{1}{2\pi} \int_0^{2\pi} d\phi \frac{2}{d^2} \int_0^d r dr \dots \quad (2)$$

where $2d$ is the distance between vortices, $d = 1/\sqrt{eH}$ [14]. Then Eq.(1) reduces to

$$N(E, H)/N_0 = \frac{4}{\pi} \frac{\epsilon}{\Delta} g\left(\frac{E}{\epsilon}\right) \simeq \frac{2v}{\pi} \sqrt{\frac{\pi}{\Phi_0}} \frac{\sqrt{H}}{\Delta} g\left(\frac{2}{v} \sqrt{\frac{\Phi_0}{\pi}} \frac{E}{\sqrt{H}}\right) \quad (3)$$

with the scaling function $g(s)$,

Fig. 1. – The scaling function $g(s)$ in Eq.(4) is shown as a function of $s = E/\epsilon$.

Fig. 2. – The specific heat data ($\diamond$) by Nishizaki *et al.*[19] is fitted with the $\sqrt{H}$ law.

$$g(s) = \begin{cases} \frac{\pi}{4}s(1 + \frac{1}{2s^2}) & \text{for } s = \frac{E}{\epsilon} \geq 1 \\ \frac{3}{4}\sqrt{1-s^2} + \frac{1}{4s}(1+2s^2)\sin^{-1}s & \text{for } s = E/\epsilon \leq 1 \end{cases} \quad (4)$$

and $\epsilon = \frac{v}{2}\sqrt{eH} = \frac{v}{2}\sqrt{\frac{\pi}{\Phi_0}}\sqrt{H}$ and Φ_0 is a quantum of flux ($\simeq 2.07 \times 10^{-11}$ T-cm²). For $E = 0$, we obtain $N(0, H)/N_0 = \frac{4}{\pi}\frac{\epsilon}{\Delta}$, since $g(s) = 1 + \frac{1}{6}s^2$ for $s \ll 1$. Also $g(s) \sim \frac{\pi}{4}s$ for $s \gg 1$ which means $N(E, H)/N_0 \simeq E/\Delta$ for the high energy excitations $E \gg \epsilon$. The scaling function $g(s)$ versus $s = \frac{E}{\epsilon} (= \frac{2}{v}\sqrt{\frac{\Phi_0}{\pi}}\frac{E}{\sqrt{H}})$ is shown in Fig. 1. A function similar to Eq.(4) has been obtained for a spherical Fermi surface in [12].

Thermodynamics. – Making use of the density of states, i.e. Eq.(3), we can determine the thermodynamic quantities at the low temperatures, $T \ll T_c$. First, the specific heat $C_s(T, H)$ is given by

$$\begin{aligned} C_s(T, H)/\gamma_n T &= \frac{3}{2\pi^2} \int_0^\infty dE E^2 \frac{N(E, H)}{N_0} \text{sech}^2\left(\frac{E}{2T}\right) \\ &= \frac{4}{\pi} \frac{\epsilon}{\Delta} f(T/\epsilon) \end{aligned} \quad (5)$$

where

$$f(T/\epsilon) = \frac{3}{2\pi^2} \left(\frac{\epsilon}{T}\right)^3 \int_0^\infty ds s^2 g(s) \text{sech}^2\left(\frac{\epsilon}{2T}s\right) \quad (6)$$

and $\gamma_n T$ is the specific heat in the normal state. We have $f(T/\epsilon) \rightarrow 1$ for $T/\epsilon \ll 1$ and $f(T/\epsilon) = \frac{27\zeta(3)}{4\pi} \frac{T}{\epsilon}$ for $T/\epsilon \gg 1$. With this limiting behavior of $f(T/\epsilon)$, the specific heat takes $C_s/\gamma_n T = \frac{4}{\pi} \frac{\epsilon}{\Delta} = \frac{2v}{\pi} \sqrt{\frac{\pi}{\Phi_0}} \frac{\sqrt{H}}{\Delta}$ at low temperature $T \ll \epsilon$ and $C_s/\gamma_n T = \frac{27\zeta(3)}{\pi^2} \frac{T}{\Delta}$ for the $H = 0$, respectively. In the limit of $T \rightarrow 0$, the $\sqrt{H}$ dependence of the specific heat in YBCO has been discussed in [7, 8, 9]. When we parameterized $C_s/T = A_c \sqrt{H}$ and the specific heat in the absence of the field $C_s(T, 0)/T = \alpha T$, we can deduce $v = \frac{27\zeta(3)}{2\pi} \sqrt{\frac{\pi}{\Phi_0}} \frac{A_c}{\alpha} \simeq 2.28 \times 10^6$ cm/s and 1.76×10^6 cm/s from [7] and [9], respectively. We may introduce an adjustable parameter a in front of v as in [12]. Then if we assume the Fermi velocity $v \simeq 10^7$ cm/s, a is about 0.2 which is the same as deduced by Chiao *et al.*[26].

In the case of Sr₂RuO₄ the recent specific heat data by Nishizaki *et al.*[19] exhibits clearly the $\sqrt{H}$ dependence as shown in Fig.2. The deviation from the $\sqrt{H}$ law for $H < 0.01T$ is most likely due to disorders.

Also Wang *et al.* [27] studied the scaling behavior of the specific heat of YBCO

$$\frac{C(T, H) - C(T, 0)}{\gamma_n T \left[\frac{4}{\pi} \frac{\epsilon}{\Delta}\right]} \equiv F\left(\frac{T}{\epsilon}\right) = f\left(\frac{T}{\epsilon}\right) - \frac{27\zeta(3)}{4\pi} \frac{T}{\epsilon}$$

Fig. 3. – The scaling function $F(T/\epsilon)$ of specific heat in Eq.(7), the scaling function $I(T/\epsilon)$ of the spin susceptibility (or the superfluid density) in Eq.(10) and the scaling function $G(T/\epsilon)$ of the nuclear spin lattice relaxation rate in Eq.(13) are shown altogether as a function of T/ϵ .

$$= \begin{cases} 1 - \frac{27\zeta(3)}{4\pi} \frac{T}{\epsilon} \frac{\pi^2}{30} (\frac{T}{\epsilon})^2 + \dots & \text{for } \frac{T}{\epsilon} \ll 1 \\ \frac{3}{2\pi} (\ln 2) (\frac{\epsilon}{T})^2 + \dots & \text{for } \frac{T}{\epsilon} \gg 1 \end{cases} \quad (7)$$

We show in Fig.3 $F(\frac{T}{\epsilon})$ versus $\frac{T}{\epsilon}$. The present model appears to describe the scaling behavior in YBCO [27] very well. Clearly a similar study of the scaling relation in the vortex state of Sr_2RuO_4 will be of great interest.

Similarly, both the spin susceptibility χ and the superfluid density ρ_s should exhibit the scaling behavior.

$$\begin{aligned} \chi(T, H)/\chi_n &= 1 - \rho_s(H, T) = \frac{1}{2T} \int_0^\infty \frac{N(E, H)}{N_0} \text{sech}^2(\frac{E}{2T}) \\ &= \frac{4}{\pi} \frac{\epsilon}{\Delta} h(T/\epsilon) \end{aligned} \quad (8)$$

and

$$h(T/\epsilon) = \frac{1}{2} \frac{\epsilon}{T} \int_0^\infty ds g(s) \text{sech}^2(\frac{\epsilon}{2T} s) \quad (9)$$

Here χ_n is the spin susceptibility in the normal state. We have $h(T/\epsilon) \rightarrow 1$ for $T/\epsilon \ll 1$ and $h(T/\epsilon) = \frac{\pi}{2} \ln 2 \frac{T}{\epsilon}$ for $T/\epsilon \gg 1$. With this limiting behavior of $h(T/\epsilon)$ both the susceptibility and superfluid density take $\sim \frac{2v}{\pi} \sqrt{\frac{\pi}{\Phi_0}} \frac{\sqrt{H}}{\Delta}$ in the limit of $T \rightarrow 0$, and $\sim 2(\ln 2) \frac{T}{\Delta}$ in the limit of $T \gg \epsilon$. As already mentioned in the introduction the $\sqrt{H}$ dependence of the susceptibility has been observed [23]. However the reported $\rho_s(T, H)$ in YBCO by muon spin rotation appears not to exhibit the $\sqrt{H}$ behavior. A further study of $\rho_s(T, H)$ is clearly desirable. Again it may be more useful to introduce the scaling function by

$$\begin{aligned} I(T/\epsilon) &\equiv \frac{\chi(T, H) - \chi(T, 0)}{\chi_n[\frac{4}{\pi} \frac{\epsilon}{\Delta}]} = h(T/\epsilon) - 2 \ln 2 (T/\epsilon) \\ &\simeq \begin{cases} 1 - 2 \ln 2 \frac{T}{\epsilon} + \dots & \text{for } \frac{T}{\epsilon} \ll 1 \\ \frac{\pi}{16} \ln(1.622 \frac{T}{\epsilon}) \frac{\epsilon}{T} & \text{for } \frac{T}{\epsilon} \gg 1 \end{cases} \end{aligned} \quad (10)$$

The scaling function $I(T/\epsilon)$ versus T/ϵ is shown in Fig.3.

Nuclear spin lattice relaxation rate. – In the superclean limit T_1^{-1} at low temperature is given by

$$\begin{aligned} T_1^{-1}(T, H)/T_{1n}^{-1} &= \frac{1}{2T} \int_0^\infty (\frac{N(E, H)}{N_0})^2 \text{sech}^2(\frac{E}{2T}) \\ &= (\frac{4}{\pi} \frac{\epsilon}{\Delta})^2 J(T/\epsilon) \end{aligned} \quad (11)$$

where

$$J(T/\epsilon) = \frac{\epsilon}{2T} \int_0^\infty ds g^2(s) \text{sech}^2(\frac{\epsilon}{2T} s) \quad (12)$$

Here T_{1n}^{-1} is the nuclear spin lattice relaxation rate in the normal state. We have $J(T/\epsilon) \rightarrow 1$ for $T/\epsilon \ll 1$ and $J(T/\epsilon) \rightarrow \frac{1}{3}(\frac{\pi^2 T}{4\epsilon})^2$ for $T/\epsilon \gg 1$. Therefore the nuclear spin lattice relaxation rate $T_1^{-1}(T, H)/T_{1n}^{-1}$ takes $\sim H$ behavior in the limit of $T \rightarrow 0$ and $\sim (\frac{T}{\Delta})^2$ in the limit of $T \gg \epsilon$. Again it is more convenient to introduce the scaling function by

$$G(T/\epsilon) \equiv \frac{T_1^{-1}(T, H) - T_1^{-1}(T, 0)}{T_{1n}^{-1}[\frac{4}{\pi} \frac{\epsilon}{\Delta}]^2} = J(T/\epsilon) - \frac{\pi^4}{48}(T/\epsilon)^2$$

$$\simeq \begin{cases} 1 - (\frac{\pi^4}{12} - \frac{\pi}{36})(\frac{T}{\epsilon})^2 + \dots & \text{for } \frac{T}{\epsilon} \ll 1 \\ \frac{\pi^2}{16} + O((\frac{\epsilon}{T})^2) & \text{for } \frac{T}{\epsilon} \gg 1 \end{cases} \quad (13)$$

We show the scaling function $G(T/\epsilon)$ in Fig.3. The detection of this scaling function will be very useful.

Planar thermal conductivity. – Following [14] the thermal conductivity in the superclean limit (i.e. $\Gamma/\Delta \ll H/H_{c2} \ll 1$) within the conducting plane in the vortex state with the field configuration of $\mathbf{H} \parallel \mathbf{c}$ is obtained as

$$\kappa(T, H)/\kappa_n = \frac{56}{5\pi}(\frac{T}{\Delta})^2 \{ \frac{20}{7\pi^2}(\frac{\epsilon}{T})^2 + (\ln[\frac{4\Delta}{3.5T\sqrt{1+(\frac{\epsilon}{1.75T})^2}}])^2 \} \quad (14)$$

where $\kappa_n = \frac{\pi^2}{6} \frac{nT}{\Gamma_m}$ is the thermal conductivity in the normal state, n the density of electrons m the electron mass, and Γ the scattering rate by impurity. In the limit of $T \rightarrow 0$, $\kappa(T, H)/\kappa_n$ reduces to $\frac{8v^2}{\pi^2 \Phi_0 \Delta^2} H$, linear in H contrary to [12]. This linear field dependence as well as the quasi-scaling behavior of κ/T^3 versus H/T^2 in Eq.(14) have not been seen in high- T_c cuprates.

On the other hand, a recent thermal conductivity data of Sr_2RuO_4 at $T = 0.35$ K exhibits a clear H -linear dependence for $H > 0.02$ T [28]. At a low magnetic field ($H < 0.015$ T) the thermal conductivity appears to be independent of H . The thermal conductivity in the superclean limit in the present model for $T > \epsilon$ becomes almost independent of H and increases like $\kappa \sim T^3 \ln(\Delta/T)$.

Further, this kind of behavior should be quite common to the unconventional superconductors with the nodal superconductors (e.g. E_{2u} -state in UPt_3 [29]). In particular when $\epsilon/T \ll 1$, κ/T^3 decreases with increasing H almost linearly in H/T^2 . Indeed this behavior has been observed in the B-phase of UPt_3 recently [29].

The low temperature thermal conductivity in high- T_c cuprates with the field $\mathbf{H} \parallel \mathbf{c}$ appears to be described by the one in the clean limit (i.e. $H/H_{c2} \ll \Gamma/\Delta \ll 1$) rather than the one in the superclean limit.

The thermal conductivity in the clean limit, on the other hand, is given by [14];

$$\kappa/\kappa_{00} = \frac{\Delta_{00}}{\Delta} \left(1 + \frac{v^2 e H}{6\pi \Gamma \Delta} \ln(4\sqrt{\frac{2\Delta}{\pi \Gamma}}) \ln(\frac{4\Delta}{v\sqrt{eH}}) \right) \quad (15)$$

Here Δ_{00} is the order parameter in the absence of the impurity scattering at $T = 0$, $\kappa_{00} = \frac{\pi}{3} \frac{T_n}{\Delta_{00} m}$ the universal thermal conductivity in the limit of $T \rightarrow 0$ and for $H = 0$. Indeed this $\sim H \ln(const./H)$ behavior is very consistent with the recent data from YBCO and Bi2212 single crystals [26]. We show such a comparison in Fig.4, where we took $\Gamma/\Gamma_c = 0.06, 0.188$, and 0.33. Here $\Gamma_c = 0.8819 T_{c0}$ is the critical scattering rate when the superconductivity disappears.

Fig. 4. – The thermal conductivity data in YBCO by Chiao *et al.* [26] are fitted with the the thermal conductivity Eq.(15) with $\Gamma/\Gamma_c = 0.06$ (—), 0.188 (- - -), 0.33 ($\cdots$), where $\square$ for $x = 0$, $\diamond$ for $x = 0.006$, $\triangle$ for $x = 0.03$ of $\text{YBa}_2(\text{Cu}_{1-x}\text{Zn}_x)_3\text{O}_{6.9}$. The $H \ln(\text{const.}/H)$ dependence describes very well the experimental data.


Concluding Remarks. – Limiting ourselves in the configuration $\mathbf{H} \parallel \mathbf{c}$ (i.e. the magnetic field normal to the conducting plane) and in the superclean limit we obtain the expression of the thermodynamic quantities and T_1^{-1} in NMR in vortex states in d -wave superconductors. Some of limiting behaviors for $T \rightarrow 0$ K have been well established in the vortex state of YBCO, though little work on the scaling behavior has been done. We have shown also the present model describes some features of the vortex state in Sr_2RuO_4 , specially the presence of the nodal structure in the order parameter. This suggest that single crystals of Sr_2RuO_4 will provide another testing ground of the present model. At the present, among three 2D f -wave states for Sr_2RuO_4 , only one of them, $\Delta(\mathbf{k}) \sim \cos(ck_3)e^{\pm i\phi}$, appears to be viable, since both the extremely small angle dependence of the upper critical field [30] and the thermal conductivity [28, 31] with the field applied parallel to the conducting plane are incompatible to other two candidates. Also, we expect similar behaviors of vortex state in other unconventional superconductors [14, 22]. Therefore the exploration of the vortex state will bring further insight in unconventional superconductors.

Acknowledgment. – First of all we thank May Chiao for providing us her Ph.D. thesis, which was very useful for the present work. Our thank also goes to Bernard Revas and Yuji Matsuda, who send us Ref.[27] and Ref.[28], respectively, prior to the publication. Finally we thank Thomas Dahm and Koichi Izawa for useful discussions on the related subjects. HW acknowledges the support from the Korean Science and Engineering Foundation through the Grant No. 1999-2-114-005-5. Also, HW thanks Dept. of Physics and Astronomy, USC for their hospitality during her stay.


REFERENCES

- [1] Maki K., Won, H. Ann. Physics, (Leipzig) 5, 320, (1996); J. Phys. I (France) 6, 2317 (1998)
- [2] Tsuei, C. C. and Kirtley, J. R., Phys. Rev. Lett. 85, 182 (2000)
- [3] Kokales, J. P., et al, Phys. Rev. Lett. **85**, 3696 (2000)
- [4] Prozorov, R., et al, Phys. Rev. Lett. 85, 3700 (2000)
- [5] Volovik, G. E., JETP Lett. 58, 469 (1983)
- [6] Won, H. and Maki, K., Europhys. Lett. 30, 421 (1995); Phys. Rev. B 53, 5927 (1996)
- [7] Moler, K. A., et al, Phys. Rev. Lett. 73, 2744 (1994); Moler, K. A., et al, Phys. Rev. B 55, 3954 (1997)
- [8] Wright, D. A., et al, Phys. Rev. Lett. 82, 1550 (1999)
- [9] Revas, B., Genoud, J. Y., Junod, A., Neumaier, K., Erb, A. and Walker, E., Phys. Rev. Lett. 80, 3364 (1998)
- [10] Sonier, J. E., et al, Phys. Rev. Lett. 83, 4156 (1999)
- [11] Barash, Yu. S., Mineev, V. P. and Svidzinskii, A. A., JETP 65, 638 (1997); Barash, Yu., S. and Svidzinskii, A. A., Phys. Rev. B 58, 476 (1998)
- [12] Kübert, C. and Hirschfeld, P. J. Sol. St. Comm 105, 439 (1998); Phys. Rev. Lett 80, 4963 (1998)
- [13] Vekhter, I., Carbotte, J. P. and Nicol, E. J., Phys. Rev. B 59, 7123 (1999); Vekhter, I., Hirschfeld, P. J., Carbotte, J. P. and Nicol, E. J., Phys. Rev. B 59, R9023 (1999)
- [14] Won, H. and Maki, K., Proceeding of NATO workshop on borocarbides (June 2000); cond-met/0004105


- [15] Carrington, A., et al, Phys. Rev. Lett. 85, 4172 (1999)
- [16] Pinteric, M., et al, Phys. Rev. B 61,7033 (2000)
- [17] Ichimura, K., Arai, T., Nomura, K., Takasaki, S., Yamada, T., Nakatsuji, S., Anzai, H., Synth. Met. 103, 1812 (1999)
- [18] Hasegawa Y., *et al.*, J. Phys. Soc. Jpn. 69, 336 (2000).
- [19] Nishizaki, S., Maeno, Y., and Mao, Z., J. Phys. Soc. Jpn. 69, 572 (2000).
- [20] Ishida, K., *et al.*, Nature 396, 658 (1998).
- [21] Bonalde, I., *et al.*, preprint.
- [22] Won, H., and Maki, K., Europhys. Lett. 52, 1427 (2000).
- [23] Zheng, G.Q., Clark, W. G., Kitaoka, Y., Asayama, K., Kodama, Y., Kuhns, P., and Moulton, W. G., Phys. Rev. B 60, R9947 (1999)
- [24] Simon, S. H. and Lee, P.A., Phys. Rev. Lett 78, 1548 (1997); *ibid* 78, 5029 (1997); Volovik, G. E. and Kopnin, N. B. *ibid* 78, 5028 (1997)
- [25] Maki, K. and Tsuneto, T., Prog. Theor. Phys. 27, 228 (1960)
- [26] Chiao, M., *et al.*, Phys. Rev. Lett. 82, 2943 (1999); Chiao, M., *et al.*, Phys. Rev. B 62, 3554 (2000).
- [27] Wang, Y., Revas, B., Erb, A. and Junod, A., cond-mat/0009194.
- [28] Izawa, K., *et al.*, preprint.
- [29] Suderow, H., Brison, J.P., Huxley, A. and Flouquet, J., Phys. Rev. Lett. 80, 165 (1998).
- [30] Mao, Z.Q., Maeno, Y., Nishizaki, S., Akima, T., and Ishiguro, T., Phys. Rev. Lett. 84, 991 (2000).
- [31] Tanatar, M.A., Nagai, S., Mao, Z.Q., Maeno, Y., Ishiguro, T., Physica C 341-348, 991 (2000).

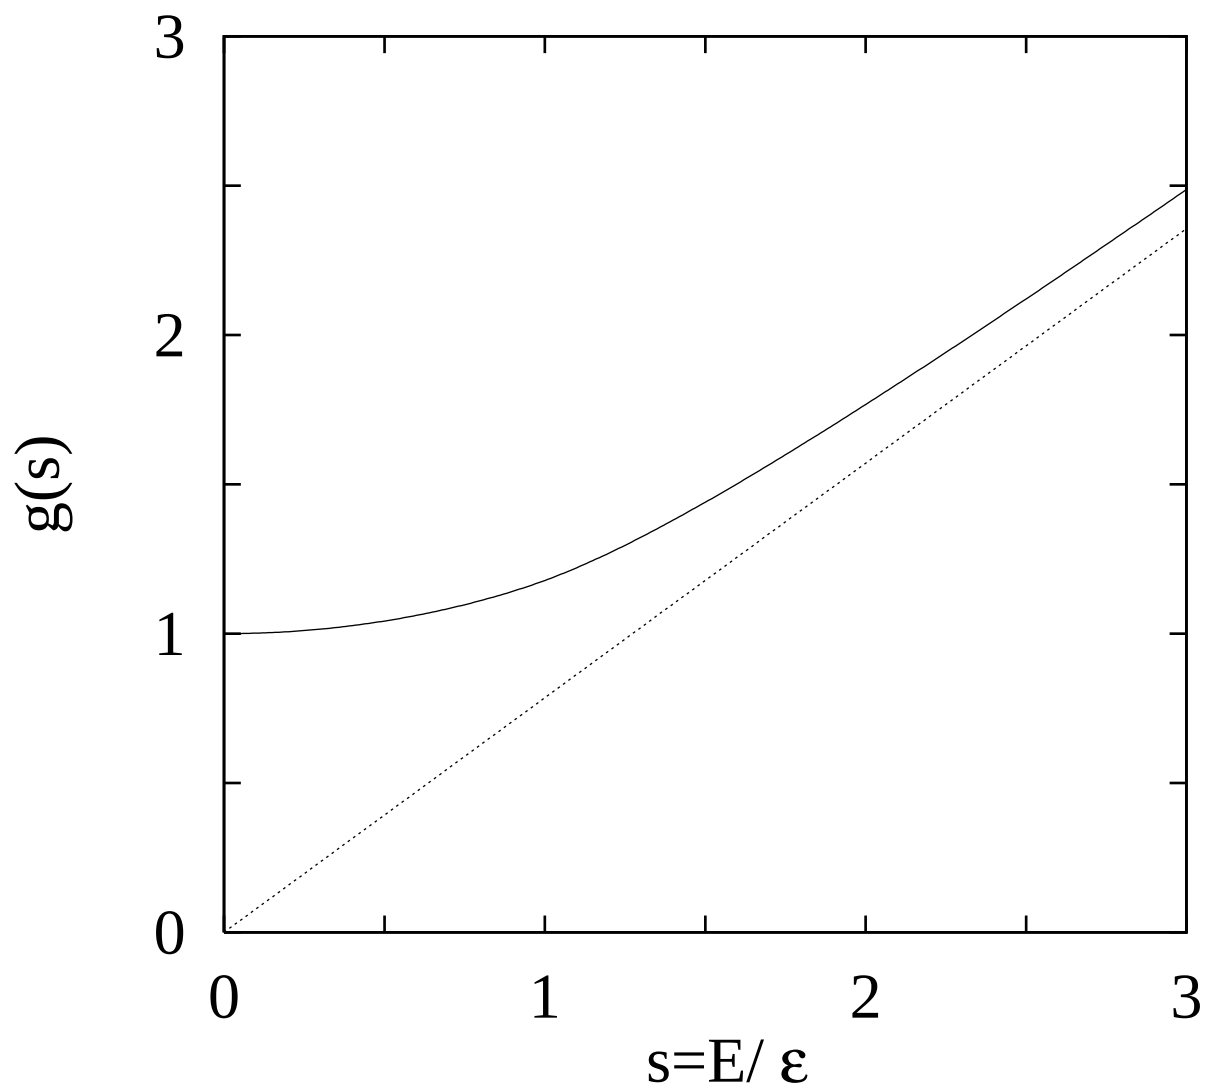


H. Won and K. Maki, Fig.1

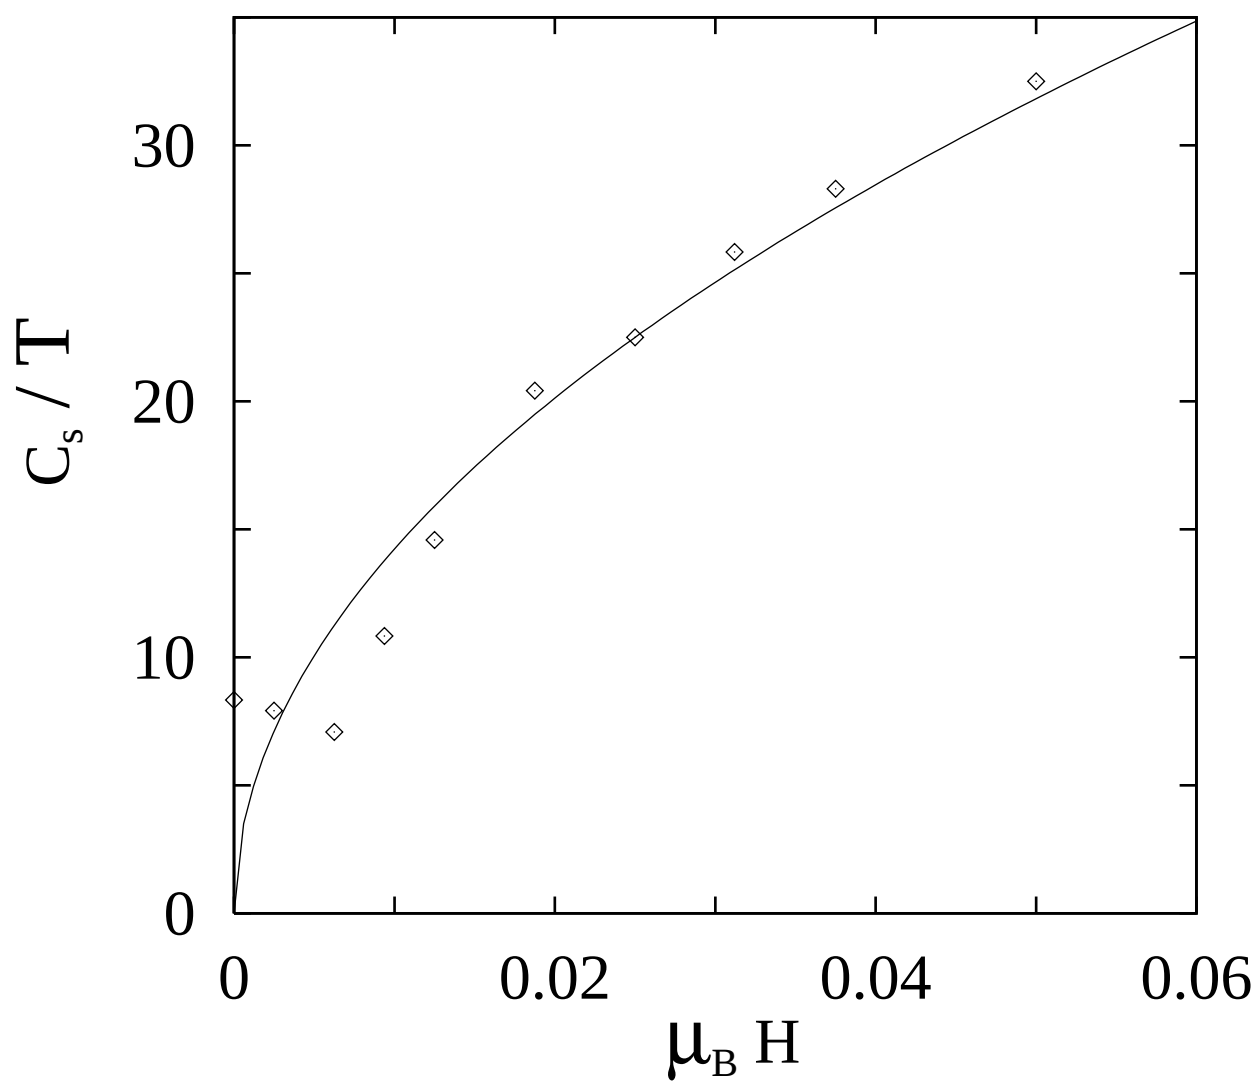

H. Won and K. Maki, Fig.2

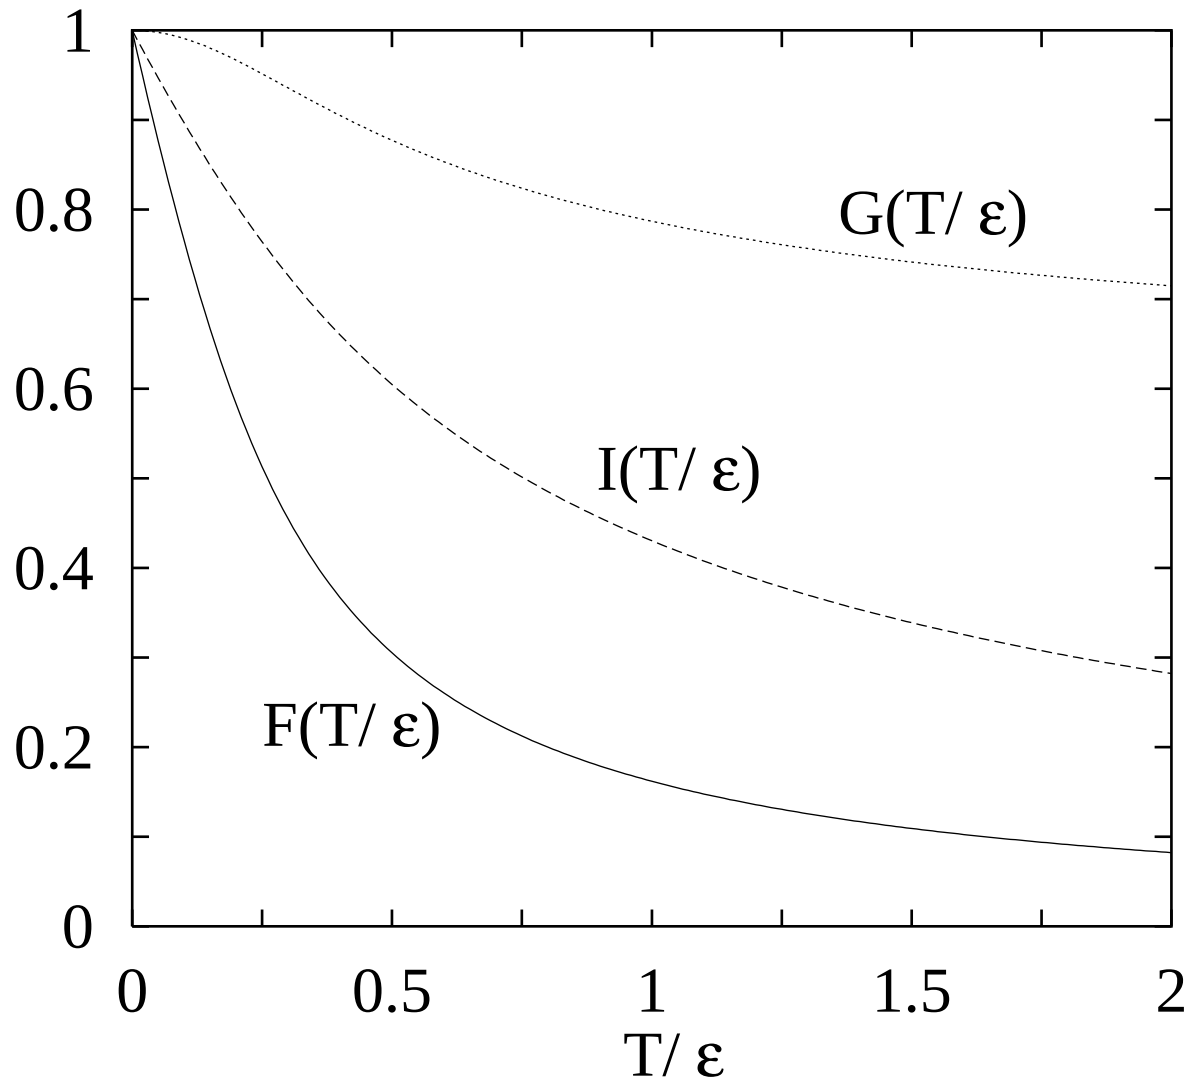

H. Won and K. Maki, Fig.3

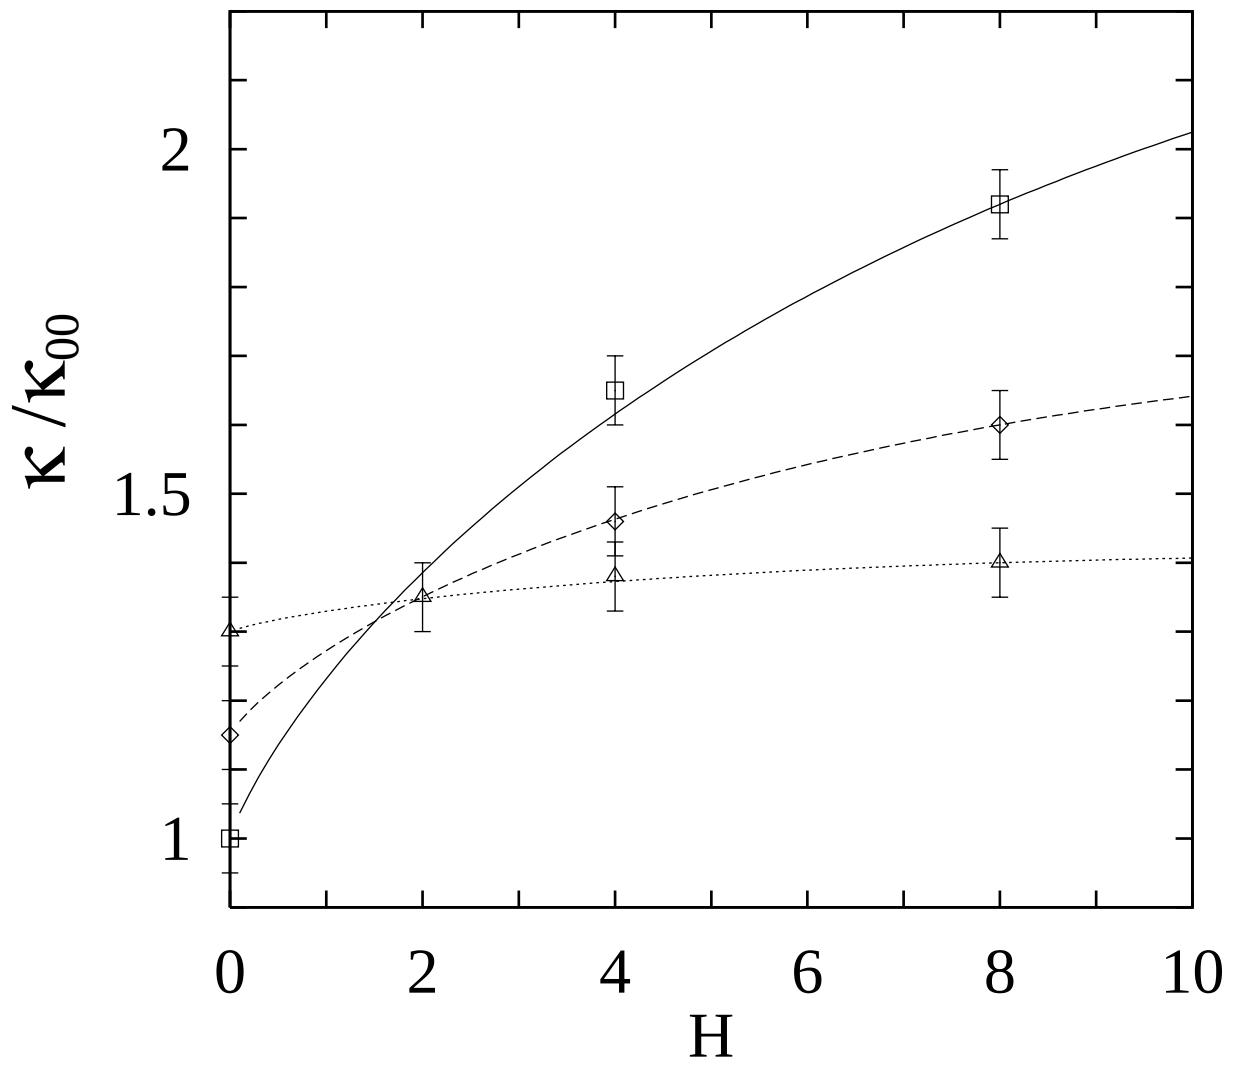

H. Won and K. Maki, Fig.4